

4-6-2018

Syntheses, Raman Spectroscopy and Crystal Structures of Alkali Hexa-fluoridorhenates(IV) Revisited

James Louis-Jean
University of Nevada, Las Vegas

Samundeeswari Mariappan Balasekaran
University of Nevada, Las Vegas, samundeeswari.mariappanbalasekaran@unlv.edu

Dean Smith
University of Nevada, Las Vegas, dean.smith@unlv.edu

Ashkan Salamat
University of Nevada, Las Vegas, ashkan.salamat@unlv.edu

Chien Thang Pham
Hanoi University of Science

Follow this and additional works at: https://digitalscholarship.unlv.edu/chem_fac_articles

 [next page for additional authors](#)
Part of the [Chemistry Commons](#)

Repository Citation

Louis-Jean, J., Mariappan Balasekaran, S., Smith, D., Salamat, A., Pham, C. T., Poineau, F. (2018). Syntheses, Raman Spectroscopy and Crystal Structures of Alkali Hexa-fluoridorhenates(IV) Revisited. *Acta Crystallographica Section E: Crystallographic Communications*, 74 646-649.
<http://dx.doi.org/10.1107/S2056989018005297>

This Article is protected by copyright and/or related rights. It has been brought to you by Digital Scholarship@UNLV with permission from the rights-holder(s). You are free to use this Article in any way that is permitted by the copyright and related rights legislation that applies to your use. For other uses you need to obtain permission from the rights-holder(s) directly, unless additional rights are indicated by a Creative Commons license in the record and/or on the work itself.

This Article has been accepted for inclusion in Chemistry and Biochemistry Faculty Publications by an authorized administrator of Digital Scholarship@UNLV. For more information, please contact digitalscholarship@unlv.edu.

Authors

James Louis-Jean, Samundeeswari Mariappan Balasekaran, Dean Smith, Ashkan Salamat, Chien Thang Pham, and Frederic Poineau



Syntheses, Raman spectroscopy and crystal structures of alkali hexafluoridorhenates(IV) revisited

James Louis-Jean,^a Samundeeswari Mariappan Balasekaran,^{a*} Dean Smith,^b Ashkan Salamat,^b Chien Thang Pham^c and Frederic Poineau^a

Received 17 December 2017

Accepted 3 April 2018

Edited by M. Weil, Vienna University of Technology, Austria

Keywords: rhenium; fluorine; crystal structure; Raman spectroscopy; isotypism.

CCDC references: 1834616; 1834615; 1834614


Supporting information: this article has supporting information at journals.iucr.org/e

^aDepartment of Chemistry, University of Nevada Las Vegas, 4505 South Maryland Parkway, Las Vegas, Nevada, 89154, United States, ^bDepartment of Physics and Astronomy and HiPSEC, University of Nevada Las Vegas, 4505 South Maryland Parkway, Las Vegas, Nevada, 89154, United States, and ^cDepartment of Chemistry, Hanoi University of Science, Hanoi, Vietnam. *Correspondence e-mail: m.b.eswari@unlv.edu

The $A_2[\text{ReF}_6]$ ($A = \text{K}, \text{Rb}$ and Cs) salts are isotypic and crystallize in the trigonal space group type $P\bar{3}m1$, adopting the $\text{K}_2[\text{GeF}_6]$ structure type. Common to all $A_2[\text{ReF}_6]$ structures are slightly distorted octahedral $[\text{ReF}_6]^{2-}$ anions with an average $\text{Re}-\text{F}$ bond length of 1.951 (8) Å. In those salts, symmetry lowering on the local $[\text{ReF}_6]^{2-}$ anions from O_h (free anion) to D_{3d} (solid-state structure) occur. The distortions of the $[\text{ReF}_6]^{2-}$ anions, as observed in their Raman spectra, are correlated to the size of the counter-cations.

1. Chemical context

The hexafluoridorhenate(IV) anion has been known for 80 years but its chemistry is understudied with respect to the heavier halogen analogs (Ruff & Kwasnik, 1934). The scarcity of $[\text{ReF}_6]^{2-}$ salts is attributed to the difficulties in their preparation and purification. $\text{K}_2[\text{ReF}_6]$ was the first hexafluoridorhenate(IV) salt to be reported; it was prepared from the solid-state melting reaction (SSMR) of $\text{K}_2[\text{ReBr}_6]$ with KHF_2 (Ruff & Kwasnik, 1934). Almost two decades later, ten salts comprising the $[\text{ReF}_6]^{2-}$ anion and with different counter-cations (Rb^+ , Cs^+ , PPh_4^+ ($\text{Ph} = \text{C}_6\text{H}_5$), $[\text{Ni}(\text{NH}_3)_6]^{2+}$, $[\text{Co}(\text{NH}_3)_6]^{3+}$, $\{[\text{Co}(\text{NH}_3)_6](\text{NO}_3)\}^{2+}$, $\{[\text{Cr}(\text{NH}_3)_6](\text{NO}_3)\}^{2+}$, $[\text{Co}(\text{NH}_3)_5\text{Cl}]^{2+}$, $[\text{Cr}(\text{NH}_3)_5\text{Cl}]^{2+}$, $[\text{Co}(\text{NH}_3)_4(\text{CO}_3)]^{2+}$) had been reported (Peacock, 1956; Weise, 1956; Pedersen *et al.*, 2014; Brauer & Allardt, 1962). Those salts were prepared by cation metathesis starting from $(\text{NH}_4)_2[\text{ReF}_6]$ or $\text{K}_2[\text{ReF}_6]$. However, the synthetic procedure to prepare $(\text{NH}_4)_2[\text{ReF}_6]$ or $\text{K}_2[\text{ReF}_6]$ was not explained in detail. To date, only the structures of two $[\text{ReF}_6]^{2-}$ salts have been characterized by single crystal X-ray diffraction (SCXRD): $\text{K}_2[\text{ReF}_6]$ (measured at 292 K) and $(\text{PPh}_4)_2[\text{ReF}_6]\cdot\text{H}_2\text{O}$ (measured at 122 K) (Clark & Russell, 1978; Pedersen *et al.*, 2014). Similarly, the synthesis of the $\text{K}_2[\text{TcF}_6]$ congener, which was reported in 1963, involves the SSMR of $\text{K}_2[\text{TcBr}_6]$ with KHF_2 followed by an aqueous work-up (Schwochau & Herr, 1963). However, $[\text{TcF}_6]^{2-}$ salts have been reinvestigated recently (Balasekaran *et al.*, 2013), and various routes for the different salts of $A_2[\text{TcF}_6]$ [$A = \text{Na}, \text{K}, \text{Rb}, \text{Cs}$ and $\text{N}(\text{CH}_3)_4$] were reported. These salts were characterized by Raman and IR spectroscopy and by SCXRD. The $A_2[\text{ReF}_6]$ salts could serve as suitable precursors to explore the chemistry of rhenium in the oxidation state IV.

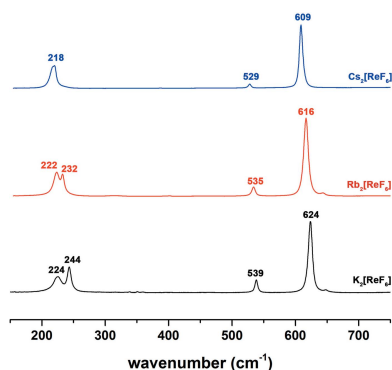

OPEN ACCESS

Table 1

 Structural details (Å, °) of the $[\text{ReF}_6]^{2-}$ anion in this study and of the related anion in $[\text{TcF}_6]^{2-}$ salts^a.


	$M-F, M = \text{Re}$	$F-M-F, M = \text{Re}$	$M-F, M = \text{Tc}$	$F-M-F, M = \text{Tc}$
$\text{K}_2[\text{MF}_6]$	1.948 (3)	86.08 (12), 93.92 (12), 180	1.928 (6)	86.93 (5), 93.07 (5), 180
$\text{Rb}_2[\text{MF}_6]$	1.945 (7)	86.5 (3), 93.5 (3), 180	1.933 (3)	87.2 (2), 92.8 (2), 180
$\text{Cs}_2[\text{MF}_6]$	1.9594 (18)	86.86 (7), 93.14 (7), 180	1.935 (5)	87.8 (2), 92.2 (2), 180

 Note: (a) Balasekaran *et al.* (2013).

Here, we revisited the synthesis of $A_2[\text{ReF}_6]$ ($A = \text{K}, \text{Rb}, \text{Cs}$) salts and report their crystal structures determined from single crystal data, and their Raman spectra.

2. Structural commentary

The title alkaline metal salts $A_2[\text{ReF}_6]$ ($A = \text{K}, \text{Rb}, \text{Cs}$) are isotypic. They adopt the $\text{K}_2[\text{GeF}_6]$ structure type (Hoard & Vincent, 1939) and crystallize in the trigonal space group type $P\bar{3}m1$ (Table 1), just like the related $A_2[\text{TcF}_6]$ ($A = \text{K}, \text{Rb}, \text{Cs}$) compounds (Balasekaran *et al.*, 2013). Selected bond lengths and angles of the series of $[\text{ReF}_6]^{2-}$ anions of the present work and the reported $[\text{TcF}_6]^{2-}$ salts (Balasekaran *et al.*, 2013) are presented in Table 1. Representative for all other title compounds, the $[\text{ReF}_6]^{2-}$ anion of the $\text{Cs}_2[\text{ReF}_6]$ salt is given in Fig. 1. The Re^{IV} atom is located on a position with site symmetry $\bar{3}m$. (Wyckoff position 1a) at the origin of the trigonal unit cell. The six symmetry-related fluorine ligands form a slightly distorted octahedral coordination sphere around the rhenium(IV) atom. The $\text{Re}-\text{F}$ bond lengths for the K, Rb, and Cs salts of $[\text{ReF}_6]^{2-}$, 1.948 (3), 1.945 (7) and 1.9594 (18) Å, respectively, are longer than the $\text{Tc}-\text{F}$ bond lengths for the congener K, Rb, and Cs salts of $[\text{TcF}_6]^{2-}$,

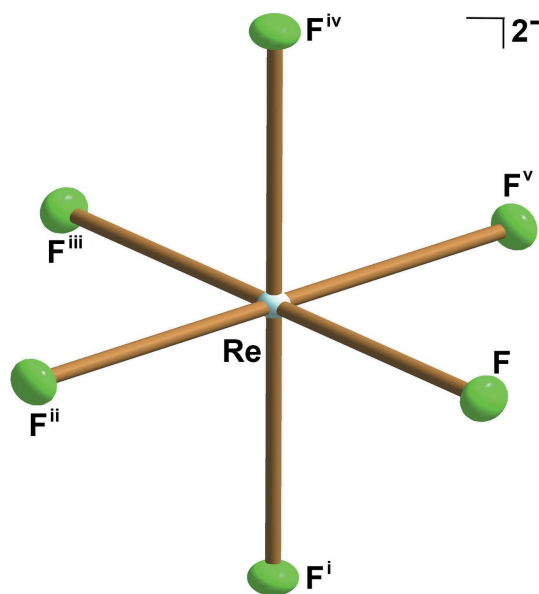
Figure 1


Representation of the $[\text{ReF}_6]^{2-}$ anion in $\text{Cs}_2[\text{ReF}_6]$. Displacement ellipsoids are drawn at the 50% probability level. [Symmetry codes: (i) $-x, -y, -z$; (ii) $x - y, x, -z$; (iii) $-x + y, -x, z$; (iv) $-y, x - y, z$; (v) $y, -x + y, -z$.]

1.928 (1), 1.933 (3), and 1.935 (5) Å, respectively (Balasekaran *et al.*, 2013).

In $A_2[\text{ReF}_6]$ ($A = \text{K}^+, \text{Rb}^+, \text{Cs}^+$), each cation is located on a position with site symmetry $3m$. (Wyckoff position 2d) and is surrounded by twelve neighboring F atoms resulting in a $[3 + 6 + 3]$ arrangement with three groups of fluoride ligands with distances of 3.0955 (19) Å (three of such), 3.1655 (6) Å (six of such), and 3.224 (2) Å (three of such) for the Cs^+ salt as a representative of the three $[\text{ReF}_6]^{2-}$ salts. These bond-length distributions are also found in the K^+ and Rb^+ salts of the $[\text{ReF}_6]^{2-}$ complexes. This correlates well and confirms that $A_2[\text{ReF}_6]$ salts are isotypic with $\text{K}_2[\text{GeF}_6]$ and the congener $A_2[\text{TcF}_6]$ ($A = \text{K}^+, \text{Rb}^+, \text{Cs}^+$) (Balasekaran *et al.*, 2013; Hoard & Vincent, 1939). In comparison with the previous structure determination of $\text{K}_2[\text{ReF}_6]$ (Clark & Russell, 1978), the current redetermination resulted in better reliability factors, together with a more precise determination of lattice parameters and atomic coordinates.

3. Raman spectroscopy

As reported previously for $\text{K}_2[\text{ReF}_6]$ and $A_2[\text{TcF}_6]$ ($A = \text{K}, \text{Rb}, \text{Cs}$) (Bettinelli *et al.*, 1987; Balasekaran *et al.*, 2013), the $[\text{ReF}_6]^{2-}$ anions are compressed along the crystallographic c axis, thus lowering the ideal molecular symmetry of the $[\text{ReF}_6]^{2-}$ anions from O_h to D_{3d} in the solid state. The representative unit-cell plot of $\text{Cs}_2[\text{ReF}_6]$ is given in Fig. 2. The effect of symmetry lowering among the alkali metal salts of $[\text{TcF}_6]^{2-}$ and its correlation with the vibrational spectra are

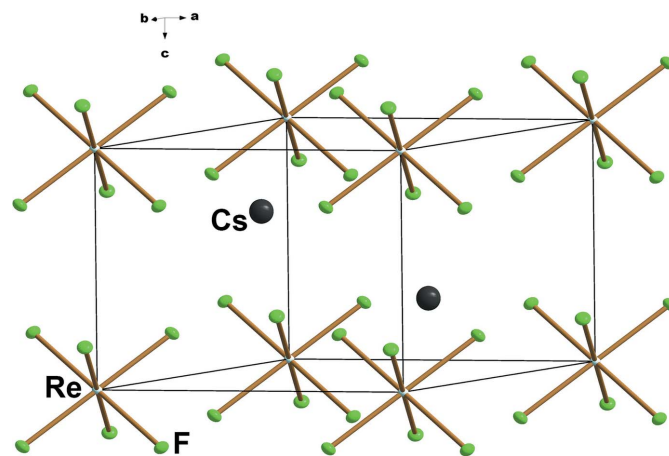
Figure 2

A packing diagram of $\text{Cs}_2[\text{ReF}_6]$. Displacement ellipsoids are drawn at the 50% probability level.

Table 2
Experimental details.

	$K_2[ReF_6]$	$Rb_2[ReF_6]$	$Cs_2[ReF_6]$
Crystal data			
M_r	378.40	471.14	566.02
Crystal system, space group	Trigonal, $P\bar{3}m1$	Trigonal, $P\bar{3}m1$	Trigonal, $P\bar{3}m1$
Temperature (K)	100	100	100
a, c (Å)	5.834 (2), 4.546 (2)	5.9926 (13), 4.7177 (10)	6.268 (1), 4.931 (1)
V (Å ³)	134.00 (11)	146.72 (7)	167.77 (6)
Z	1	1	1
Radiation type	Mo $K\alpha$	Mo $K\alpha$	Mo $K\alpha$
μ (mm ⁻¹)	24.26	37.22	28.83
Crystal size (mm)	0.10 × 0.07 × 0.04	0.08 × 0.07 × 0.04	0.25 × 0.12 × 0.11
Data collection			
Diffractometer	Bruker D8 QUEST	Bruker D8 QUEST	Bruker D8 QUEST
Absorption correction	Multi-scan (SADABS; Bruker, 2015)	Numerical (SADABS; Bruker, 2015)	Multi-scan (SADABS; Bruker, 2015)
T_{min}, T_{max}	0.14, 0.44	0.11, 0.30	0.05, 0.15
No. of measured, independent and observed [$I > 2\sigma(I)$] reflections	2148, 180, 180	1526, 115, 111	2683, 218, 218
R_{int}	0.054	0.073	0.040
$(\sin \theta/\lambda)_{max}$ (Å ⁻¹)	0.714	0.593	0.713
Refinement			
$R[F^2 > 2\sigma(F^2)], wR(F^2), S$	0.016, 0.041, 1.13	0.027, 0.074, 1.30	0.013, 0.036, 1.25
No. of reflections	180	115	218
No. of parameters	12	12	13
$\Delta\rho_{max}, \Delta\rho_{min}$ (e Å ⁻³)	1.80, -1.37	1.91, -1.36	0.68, -2.92

Computer programs: APEX3 and SAINT (Bruker, 2015), SHELXS (Sheldrick, 2008), SHELXL2014 (Sheldrick, 2015), DIAMOND (Brandenburg, 2007) and publCIF (Westrip, 2010).

well described (Balasekaran *et al.*, 2013). Here, a similar trend occurs for the $A_2[ReF_6]$ series ($A = K, Rb, Cs$; Fig. 3). In the case of $K_2[ReF_6]$, the Raman spectrum exhibits four bands at 624, 539, 244 and 224 cm⁻¹. The latter two vibrations correspond to the F_{2g} band split due to the symmetry lowering. In the Raman spectra of $A_2[MF_6]$ complexes ($A = K, Rb, Cs; M = Tc, Re$), the F_{2g} splitting decreases from $K_2[ReF_6]$ to

$Cs_2[ReF_6]$ due to differences in $M-F$ bond length. Furthermore, the slight increase of $M-F$ bond lengths from $K_2[MF_6]$ to $Cs_2[MF_6]$ are well represented in the Raman spectra which causes the Raman bands to shift to lower wavenumbers.

4. Synthesis and crystallization

Ammonium perrhenate, ammonium bifluoride, potassium fluoride, rubidium fluoride, cesium fluoride, and hydrobromic acid (48%) were purchased from Sigma Aldrich and used without any further purification. This work was performed in a well-ventilated fume hood due to the corrosive nature of bifluoride. $K_2[ReBr_6]$ was prepared as described in the literature (Watt *et al.*, 1963), and the detailed synthesis of $A_2[ReF_6]$ ($A = K, Rb, Cs$) is described below. Single crystals of $A_2[ReF_6]$ ($A = K, Rb, Cs$) were obtained by slow evaporation at room temperature of an aqueous solution of the respective salt.

Synthesis of $K_2[ReF_6]$

$K_2[ReF_6]$ was prepared by melting $K_2[ReBr_6]$ (2 g, 2.69 mmol) with excess KHF_2 (14 g, 0.18 mol) in a nickel crucible at 673 K for 30 min in a box furnace. The resulting greyish solid product formed was allowed to cool to room temperature and was washed first with MeOH (4 × 10 ml). Subsequently, the product was washed with several aliquots of an H₂O/MeOH mixture (3 × 5 ml, 1:4 volume ratios) and centrifuged. The pink solid obtained was dissolved in warm water (5–10 ml, 353 K) and evaporated slowly at room temperature. The resultant pink crystals of $K_2[ReF_6]$ were recrystallized from warm water (5 ml, 353 K) and colorless

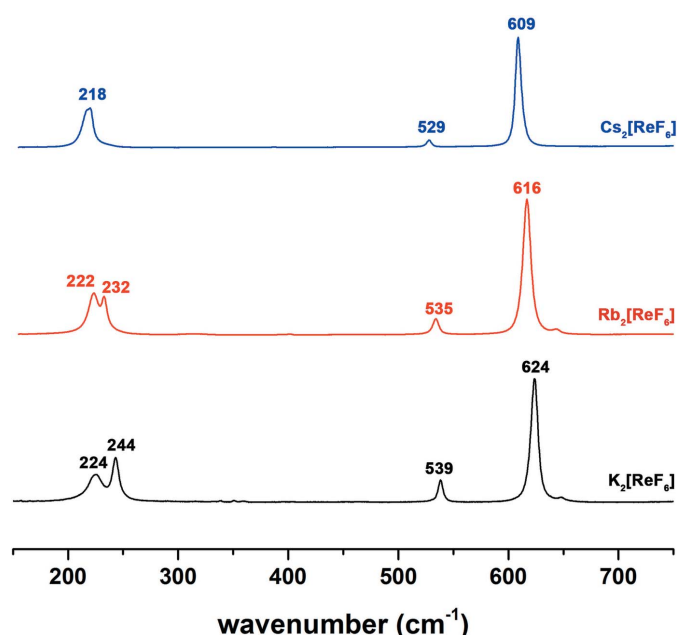


Figure 3
Raman spectra of $A_2[ReF_6]$ ($A = K, Rb, Cs$).

crystals of $K_2[ReF_6]$ were obtained. Yield: 661 mg, 1.7 mmol (65%). IR (KBr, cm^{-1}): 518, 484 sh (Re–F).

Syntheses of $A_2[ReF_6]$ (A = Rb, Cs) salts

$K_2[ReF_6]$ (151 mg, 0.4 mmol) was dissolved in 4 ml of hot water (353 K). MF ($M = Rb, Cs$) (0.8 mmol) dissolved in 1 ml of hot water (353 K) was added dropwise. The solution was allowed to evaporate slowly at room temperature. Crystals of $Rb_2[ReF_6]$ and $Cs_2[ReF_6]$ were formed in 24 h and washed first with cold water (3×2 ml) to remove other fluoride impurities followed by isopropanol (3×1 ml), and diethyl ether (3×1 ml). $Rb_2[ReF_6]$ yield: 156 mg, 0.33 mmol (83%). IR (KBr, cm^{-1}): 521 (Re–F). $Cs_2[ReF_6]$ yield: 175 mg, 0.276 mmol (77%). IR (KBr, cm^{-1}): 507, 480 sh (Re–F).

IR spectra were measured on a Shimadzu IR Affinity-1 spectrometer between 400 and 4000 cm^{-1} . Raman spectra were recorded on a HORIBA T64000 triple spectrometer operating at 30 mW in subtractive mode. The spectra were taken from pure single crystals at room temperature using the 514.5 nm (Kr/Ar) laser line.

5. Refinement

Crystal data, data collection and structure refinement details are summarized in Table 2.

Acknowledgements

The authors thank Ms Julie Bertoia and Mr Charles Bynum for laboratory support, and Ms Wendee Johns for administrative support.

Funding information

Funding for this research was provided by: Department of Energy - Nuclear Science and Security Consortium (award No. DE-NA0003180).

References

- Balasekaran, S. M., Molski, M., Spandl, J., Hagenbach, A., Alberto, R. & Abram, U. (2013). *Inorg. Chem.* **52**, 7094–7099.
- Bettinelli, M., Disipio, L., Ingleto, G. & Razzetti, C. (1987). *Inorg. Chim. Acta*, **133**, 7–9.
- Brandenburg, K. (2007). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Brauer, G. & Allardt, H. D. (1962). *Z. Anorg. Allg. Chem.* **316**, 134–140.
- Bruker (2015). *APEX3, SAINT and SADABS*. Bruker AXS Inc., Madison, WI, USA.
- Clark, G. R. & Russell, D. R. (1978). *Acta Cryst.* **B34**, 894–895.
- Hoard, J. L. & Vincent, W. B. (1939). *J. Am. Chem. Soc.* **61**, 2849–2852.
- Peacock, R. D. (1956). *J. Chem. Soc.* pp. 1291–1293.
- Pedersen, K. S., Sigrist, M., Sorensen, M. A., Barra, A. L., Weyhermuller, T., Piligkos, S., Thuesen, C. A., Vinum, M. G., Mutka, H., Weihe, H., Clerac, R. & Bendix, J. (2014). *Angew. Chem. Int. Ed.* **53**, 1351–1354.
- Ruff, O. & Kwasnik, W. (1934). *Z. Anorg. Allg. Chem.* **219**, 65–81.
- Schwochau, K. & Herr, W. (1963). *Angew. Chem.* **75**, 95.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Sheldrick, G. M. (2015). *Acta Cryst.* **C71**, 3–8.
- Watt, G. W., Thompson, R. J. & Gibbons, J. M. (1963). *Inorganic Syntheses* edited by J. Kleinberg, Vol 7, pp. 189–190. New York: McGraw-Hill.
- Weise, E. (1956). *Z. Anorg. Allg. Chem.* **283**, 377–389.
- Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.

supporting information

Acta Cryst. (2018). E74, 646-649 [https://doi.org/10.1107/S2056989018005297]

Syntheses, Raman spectroscopy and crystal structures of alkali hexafluoridorhenates(IV) revisited

James Louis-Jean, Samundeeswari Mariappan Balasekaran, Dean Smith, Ashkan Salamat, Chien Thang Pham and Frederic Poineau

Computing details

For all structures, data collection: *APEX3* (Bruker, 2015); cell refinement: *SAINTE* (Bruker, 2015); data reduction: *SAINTE* (Bruker, 2015); program(s) used to solve structure: *SHELXS* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL2014* (Sheldrick, 2015); molecular graphics: *DIAMOND* (Brandenburg, 2007); software used to prepare material for publication: *publCIF* (Westrip, 2010).

Dipotassium hexafluoridorhenate(IV) (SMB_K2ReF6_1)

Crystal data

$\text{K}_2[\text{ReF}_6]$

$M_r = 378.40$

Trigonal, $P\bar{3}m1$

$a = 5.834(2) \text{ \AA}$

$c = 4.546(2) \text{ \AA}$

$V = 134.00(11) \text{ \AA}^3$

$Z = 1$

$F(000) = 167$

$D_x = 4.689 \text{ Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Cell parameters from 2236 reflections

$\theta = 4.0\text{--}30.5^\circ$

$\mu = 24.26 \text{ mm}^{-1}$

$T = 100 \text{ K}$

Hexagonal, translucent colourless

$0.10 \times 0.07 \times 0.04 \text{ mm}$

Data collection

Bruker D8 QUEST
diffractometer

Radiation source: sealed tube, Siemens
KFFMo2K-90

Curved graphite monochromator

Detector resolution: $8.3333 \text{ pixels mm}^{-1}$

φ and ω scans

Absorption correction: multi-scan
(*SADABS*; Bruker, 2015)

$T_{\min} = 0.14$, $T_{\max} = 0.44$

2148 measured reflections

180 independent reflections

180 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.054$

$\theta_{\max} = 30.5^\circ$, $\theta_{\min} = 4.0^\circ$

$h = -8 \rightarrow 8$

$k = -8 \rightarrow 8$

$l = -6 \rightarrow 6$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.016$

$wR(F^2) = 0.041$

$S = 1.13$

180 reflections

12 parameters

0 restraints

Primary atom site location: structure-invariant
direct methods

Secondary atom site location: difference Fourier
map

$w = 1/[\sigma^2(F_o^2) + (0.0194P)^2 + 0.517P]$

where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} < 0.001$

$\Delta\rho_{\max} = 1.80 \text{ e \AA}^{-3}$

$\Delta\rho_{\min} = -1.37 \text{ e \AA}^{-3}$

Special details

Geometry. All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Re1	0	0	0	0.00863 (14)
F1	0.3254 (6)	0.1627 (3)	0.2299 (6)	0.0137 (5)
K1	0.3333	0.6667	0.2955 (4)	0.0111 (3)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Re1	0.00883 (16)	0.00883 (16)	0.0082 (2)	0.00441 (8)	0	0
F1	0.0119 (13)	0.0162 (10)	0.0117 (12)	0.0060 (6)	-0.0012 (10)	-0.0006 (5)
K1	0.0118 (5)	0.0118 (5)	0.0096 (6)	0.0059 (2)	0	0

Geometric parameters (\AA , $^\circ$)

Re1—F1	1.948 (3)	F1—K1 ^{viii}	2.9325 (10)
Re1—F1 ⁱ	1.948 (3)	F1—K1 ^{vi}	2.946 (3)
Re1—F1 ⁱⁱ	1.948 (3)	K1—F1 ^{xi}	2.762 (3)
Re1—F1 ⁱⁱⁱ	1.948 (3)	K1—F1 ^x	2.762 (3)
Re1—F1 ^{iv}	1.948 (3)	K1—F1 ^{xii}	2.762 (3)
Re1—F1 ^v	1.948 (3)	K1—F1 ^{xiii}	2.9325 (11)
Re1—K1 ⁱ	3.6263 (13)	K1—F1 ^{xiv}	2.9325 (10)
Re1—K1 ^{vi}	3.6263 (13)	K1—F1 ^{iv}	2.9325 (11)
Re1—K1 ^{vii}	3.6263 (13)	K1—F1 ^{xv}	2.9325 (11)
Re1—K1	3.6263 (13)	K1—F1 ^{xvi}	2.9325 (11)
Re1—K1 ^{viii}	3.6263 (13)	K1—F1 ^{xvii}	2.946 (3)
Re1—K1 ^{ix}	3.6263 (13)	K1—F1 ⁱⁱ	2.946 (3)
F1—K1 ^x	2.762 (3)	K1—F1 ^{vi}	2.946 (3)
F1—K1	2.9325 (11)		
F1—Re1—F1 ⁱ	180.0	K1—F1—K1 ^{viii}	168.22 (13)
F1—Re1—F1 ⁱⁱ	86.08 (12)	Re1—F1—K1 ^{vi}	93.38 (11)
F1 ⁱ —Re1—F1 ⁱⁱ	93.92 (12)	K1 ^x —F1—K1 ^{vi}	105.55 (10)
F1—Re1—F1 ⁱⁱⁱ	93.92 (12)	K1—F1—K1 ^{vi}	94.27 (6)
F1 ⁱ —Re1—F1 ⁱⁱⁱ	86.08 (12)	K1 ^{viii} —F1—K1 ^{vi}	94.27 (6)
F1 ⁱⁱ —Re1—F1 ⁱⁱⁱ	180.00 (19)	F1 ^{xi} —K1—F1 ^x	65.46 (11)
F1—Re1—F1 ^{iv}	93.92 (12)	F1 ^{xi} —K1—F1 ^{xii}	65.46 (11)
F1 ⁱ —Re1—F1 ^{iv}	86.08 (12)	F1 ^x —K1—F1 ^{xii}	65.46 (11)
F1 ⁱⁱ —Re1—F1 ^{iv}	86.08 (12)	F1 ^{xi} —K1—F1 ^{xiii}	62.44 (10)
F1 ⁱⁱⁱ —Re1—F1 ^{iv}	93.92 (12)	F1 ^x —K1—F1 ^{xiii}	127.81 (6)
F1—Re1—F1 ^v	86.08 (12)	F1 ^{xii} —K1—F1 ^{xiii}	95.05 (6)

F1 ⁱ —Re1—F1 ^v	93.92 (12)	F1 ^{xi} —K1—F1 ^{xiv}	62.44 (10)
F1 ⁱⁱ —Re1—F1 ^v	93.92 (12)	F1 ^x —K1—F1 ^{xiv}	95.05 (6)
F1 ⁱⁱⁱ —Re1—F1 ^v	86.08 (12)	F1 ^{xii} —K1—F1 ^{xiv}	127.81 (6)
F1 ^{iv} —Re1—F1 ^v	180.00 (7)	F1 ^{xiii} —K1—F1 ^{xiv}	58.10 (11)
F1—Re1—K1 ⁱ	126.206 (14)	F1 ^{xi} —K1—F1 ^{iv}	95.05 (6)
F1 ⁱ —Re1—K1 ⁱ	53.794 (14)	F1 ^x —K1—F1 ^{iv}	127.81 (6)
F1 ⁱⁱ —Re1—K1 ⁱ	125.81 (9)	F1 ^{xii} —K1—F1 ^{iv}	62.44 (10)
F1 ⁱⁱⁱ —Re1—K1 ⁱ	54.19 (9)	F1 ^{xiii} —K1—F1 ^{iv}	61.22 (12)
F1 ^{iv} —Re1—K1 ⁱ	126.205 (14)	F1 ^{xiv} —K1—F1 ^{iv}	118.98 (2)
F1 ^v —Re1—K1 ⁱ	53.795 (14)	F1 ^{xi} —K1—F1 ^{xv}	95.05 (6)
F1—Re1—K1 ^{vi}	54.19 (9)	F1 ^x —K1—F1 ^{xv}	62.44 (10)
F1 ⁱ —Re1—K1 ^{vi}	125.81 (9)	F1 ^{xii} —K1—F1 ^{xv}	127.81 (6)
F1 ⁱⁱ —Re1—K1 ^{vi}	53.794 (14)	F1 ^{xiii} —K1—F1 ^{xv}	118.98 (2)
F1 ⁱⁱⁱ —Re1—K1 ^{vi}	126.206 (14)	F1 ^{xiv} —K1—F1 ^{xv}	61.22 (12)
F1 ^{iv} —Re1—K1 ^{vi}	126.205 (14)	F1 ^{iv} —K1—F1 ^{xv}	168.22 (13)
F1 ^v —Re1—K1 ^{vi}	53.795 (14)	F1 ^{xi} —K1—F1 ^{xvi}	127.81 (6)
K1 ⁱ —Re1—K1 ^{vi}	107.11 (3)	F1 ^x —K1—F1 ^{xvi}	62.44 (10)
F1—Re1—K1 ^{vii}	125.81 (9)	F1 ^{xii} —K1—F1 ^{xvi}	95.05 (6)
F1 ⁱ —Re1—K1 ^{vii}	54.19 (9)	F1 ^{xiii} —K1—F1 ^{xvi}	168.22 (13)
F1 ⁱⁱ —Re1—K1 ^{vii}	126.206 (14)	F1 ^{xiv} —K1—F1 ^{xvi}	118.98 (2)
F1 ⁱⁱⁱ —Re1—K1 ^{vii}	53.794 (14)	F1 ^{iv} —K1—F1 ^{xvi}	118.98 (2)
F1 ^{iv} —Re1—K1 ^{vii}	53.795 (14)	F1 ^{xv} —K1—F1 ^{xvi}	58.10 (11)
F1 ^v —Re1—K1 ^{vii}	126.205 (14)	F1 ^{xi} —K1—F1	127.81 (6)
K1 ⁱ —Re1—K1 ^{vii}	72.89 (3)	F1 ^x —K1—F1	95.05 (6)
K1 ^{vi} —Re1—K1 ^{vii}	180.0	F1 ^{xii} —K1—F1	62.44 (10)
F1—Re1—K1	53.794 (14)	F1 ^{xiii} —K1—F1	118.98 (2)
F1 ⁱ —Re1—K1	126.206 (14)	F1 ^{xiv} —K1—F1	168.22 (13)
F1 ⁱⁱ —Re1—K1	54.19 (9)	F1 ^{iv} —K1—F1	58.09 (11)
F1 ⁱⁱⁱ —Re1—K1	125.81 (9)	F1 ^{xv} —K1—F1	118.98 (2)
F1 ^{iv} —Re1—K1	53.794 (14)	F1 ^{xvi} —K1—F1	61.22 (11)
F1 ^v —Re1—K1	126.206 (14)	F1 ^{xi} —K1—F1 ^{xvii}	105.55 (10)
K1 ⁱ —Re1—K1	180.0	F1 ^x —K1—F1 ^{xvii}	144.70 (4)
K1 ^{vi} —Re1—K1	72.89 (3)	F1 ^{xii} —K1—F1 ^{xvii}	144.70 (4)
K1 ^{vii} —Re1—K1	107.11 (3)	F1 ^{xiii} —K1—F1 ^{xvii}	53.80 (10)
F1—Re1—K1 ^{viii}	53.795 (14)	F1 ^{xiv} —K1—F1 ^{xvii}	53.80 (10)
F1 ⁱ —Re1—K1 ^{viii}	126.205 (14)	F1 ^{iv} —K1—F1 ^{xvii}	85.73 (6)
F1 ⁱⁱ —Re1—K1 ^{viii}	126.206 (14)	F1 ^{xv} —K1—F1 ^{xvii}	85.73 (6)
F1 ⁱⁱⁱ —Re1—K1 ^{viii}	53.794 (14)	F1 ^{xvi} —K1—F1 ^{xvii}	114.69 (6)
F1 ^{iv} —Re1—K1 ^{viii}	125.81 (9)	F1—K1—F1 ^{xvii}	114.69 (6)
F1 ^v —Re1—K1 ^{viii}	54.19 (9)	F1 ^{xi} —K1—F1 ⁱⁱ	144.70 (4)
K1 ⁱ —Re1—K1 ^{viii}	72.90 (3)	F1 ^x —K1—F1 ⁱⁱ	144.70 (4)
K1 ^{vi} —Re1—K1 ^{viii}	72.90 (3)	F1 ^{xii} —K1—F1 ⁱⁱ	105.55 (10)
K1 ^{vii} —Re1—K1 ^{viii}	107.10 (3)	F1 ^{xiii} —K1—F1 ⁱⁱ	85.73 (6)
K1—Re1—K1 ^{viii}	107.10 (3)	F1 ^{xiv} —K1—F1 ⁱⁱ	114.69 (6)
F1—Re1—K1 ^{ix}	126.205 (14)	F1 ^{iv} —K1—F1 ⁱⁱ	53.80 (10)
F1 ⁱ —Re1—K1 ^{ix}	53.795 (14)	F1 ^{xv} —K1—F1 ⁱⁱ	114.69 (6)
F1 ⁱⁱ —Re1—K1 ^{ix}	53.794 (14)	F1 ^{xvi} —K1—F1 ⁱⁱ	85.73 (6)
F1 ⁱⁱⁱ —Re1—K1 ^{ix}	126.206 (14)	F1—K1—F1 ⁱⁱ	53.80 (10)

F1 ^{iv} —Re1—K1 ^{ix}	54.19 (9)	F1 ^{xvii} —K1—F1 ⁱⁱ	60.91 (10)
F1 ^v —Re1—K1 ^{ix}	125.81 (9)	F1 ^{xi} —K1—F1 ^{vi}	144.70 (4)
K1 ⁱ —Re1—K1 ^{ix}	107.10 (3)	F1 ^x —K1—F1 ^{vi}	105.55 (10)
K1 ^{vi} —Re1—K1 ^{ix}	107.10 (3)	F1 ^{xii} —K1—F1 ^{vi}	144.70 (4)
K1 ^{vii} —Re1—K1 ^{ix}	72.90 (3)	F1 ^{xiii} —K1—F1 ^{vi}	114.69 (6)
K1—Re1—K1 ^{ix}	72.90 (3)	F1 ^{xiv} —K1—F1 ^{vi}	85.73 (6)
K1 ^{viii} —Re1—K1 ^{ix}	180.0	F1 ^{iv} —K1—F1 ^{vi}	114.69 (6)
Re1—F1—K1 ^x	161.08 (14)	F1 ^{xv} —K1—F1 ^{vi}	53.80 (10)
Re1—F1—K1	93.79 (6)	F1 ^{xvi} —K1—F1 ^{vi}	53.80 (10)
K1 ^x —F1—K1	84.95 (6)	F1—K1—F1 ^{vi}	85.73 (6)
Re1—F1—K1 ^{viii}	93.79 (6)	F1 ^{xvii} —K1—F1 ^{vi}	60.91 (10)
K1 ^x —F1—K1 ^{viii}	84.95 (6)	F1 ⁱⁱ —K1—F1 ^{vi}	60.91 (10)

Symmetry codes: (i) $-x, -y, -z$; (ii) $x-y, x, -z$; (iii) $-x+y, -x, z$; (iv) $-y, x-y, z$; (v) $y, -x+y, -z$; (vi) $-x+1, -y+1, -z$; (vii) $x-1, y-1, z$; (viii) $x, y-1, z$; (ix) $-x, -y+1, -z$; (x) $-x+1, -y+1, -z+1$; (xi) $y, -x+y+1, -z+1$; (xii) $x-y, x, -z+1$; (xiii) $-x+y, -x+1, z$; (xiv) $x, y+1, z$; (xv) $-y+1, x-y+1, z$; (xvi) $-x+y+1, -x+1, z$; (xvii) $y, -x+y+1, -z$.

Dirubidium hexafluoridorhenate(IV) (SMB_Rb2ReF6_j)

Crystal data

Rb₂[ReF₆]
 $M_r = 471.14$
 Trigonal, $P\bar{3}m1$
 $a = 5.9926$ (13) Å
 $c = 4.7177$ (10) Å
 $V = 146.72$ (7) Å³
 $Z = 1$
 $F(000) = 203$

$D_x = 5.332$ Mg m⁻³
 Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å
 Cell parameters from 1612 reflections
 $\theta = 3.9\text{--}28.3^\circ$
 $\mu = 37.22$ mm⁻¹
 $T = 100$ K
 Hexagonal plate, translucent colourless
 0.08 × 0.07 × 0.04 mm

Data collection

Bruker D8 QUEST
 diffractometer
 Radiation source: sealed tube, Siemens
 KFFMo2K-90
 Curved graphite monochromator
 Detector resolution: 8.3333 pixels mm⁻¹
 φ and ω scans
 Absorption correction: numerical
 (SADABS; Bruker, 2015)

$T_{\min} = 0.11$, $T_{\max} = 0.30$
 1526 measured reflections
 115 independent reflections
 111 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.073$
 $\theta_{\max} = 24.9^\circ$, $\theta_{\min} = 3.9^\circ$
 $h = -7 \rightarrow 7$
 $k = -7 \rightarrow 7$
 $l = -5 \rightarrow 5$

Refinement

Refinement on F^2
 Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.027$
 $wR(F^2) = 0.074$
 $S = 1.30$
 115 reflections
 12 parameters
 0 restraints

Primary atom site location: heavy-atom method
 Secondary atom site location: difference Fourier
 map
 $w = 1/[\sigma^2(F_o^2) + (0.0175P)^2 + 3.5548P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} < 0.001$
 $\Delta\rho_{\max} = 1.91$ e Å⁻³
 $\Delta\rho_{\min} = -1.36$ e Å⁻³

Special details

Geometry. All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Re1	0	0	0	0.0157 (5)
F1	0.3151 (14)	0.1576 (7)	0.2231 (15)	0.0151 (17)
Rb1	0.3333	0.6667	0.2971 (4)	0.0138 (6)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Re1	0.0133 (6)	0.0133 (6)	0.0205 (8)	0.0066 (3)	0	0
F1	0.015 (4)	0.017 (3)	0.012 (3)	0.0077 (19)	0.001 (3)	0.0007 (14)
Rb1	0.0131 (8)	0.0131 (8)	0.0152 (12)	0.0065 (4)	0	0

Geometric parameters (\AA , $^\circ$)

Re1—F1 ⁱ	1.945 (7)	F1—Rb1 ^{viii}	3.0181 (11)
Re1—F1 ⁱⁱ	1.945 (7)	F1—Rb1 ^{vi}	3.058 (7)
Re1—F1 ⁱⁱⁱ	1.945 (7)	Rb1—F1 ^{xi}	2.907 (7)
Re1—F1 ^{iv}	1.945 (7)	Rb1—F1 ^x	2.907 (7)
Re1—F1 ^v	1.945 (7)	Rb1—F1 ^{xii}	2.907 (7)
Re1—F1	1.945 (7)	Rb1—F1 ^{xiii}	3.0181 (11)
Re1—Rb1 ⁱ	3.7330 (10)	Rb1—F1 ^{xiv}	3.0181 (11)
Re1—Rb1 ^{vi}	3.7330 (11)	Rb1—F1 ^v	3.0181 (11)
Re1—Rb1 ^{vii}	3.7330 (11)	Rb1—F1 ^{xv}	3.0181 (11)
Re1—Rb1	3.7330 (10)	Rb1—F1 ^{xvi}	3.0181 (11)
Re1—Rb1 ^{viii}	3.7330 (11)	Rb1—F1 ^{xvii}	3.058 (7)
Re1—Rb1 ^{ix}	3.7330 (11)	Rb1—F1 ⁱⁱ	3.058 (7)
F1—Rb1 ^x	2.907 (7)	Rb1—F1 ^{vi}	3.058 (7)
F1—Rb1	3.0181 (11)		
F1 ⁱ —Re1—F1 ⁱⁱ	93.5 (3)	Rb1—F1—Rb1 ^{viii}	166.2 (3)
F1 ⁱ —Re1—F1 ⁱⁱⁱ	86.5 (3)	Re1—F1—Rb1 ^{vi}	93.9 (2)
F1 ⁱⁱ —Re1—F1 ⁱⁱⁱ	180.0 (3)	Rb1 ^x —F1—Rb1 ^{vi}	104.5 (2)
F1 ⁱ —Re1—F1 ^{iv}	93.5 (3)	Rb1—F1—Rb1 ^{vi}	94.26 (14)
F1 ⁱⁱ —Re1—F1 ^{iv}	93.5 (3)	Rb1 ^{viii} —F1—Rb1 ^{vi}	94.26 (14)
F1 ⁱⁱⁱ —Re1—F1 ^{iv}	86.5 (3)	F1 ^{xi} —Rb1—F1 ^x	65.8 (2)
F1 ⁱ —Re1—F1 ^v	86.5 (3)	F1 ^{xi} —Rb1—F1 ^{xii}	65.8 (2)
F1 ⁱⁱ —Re1—F1 ^v	86.5 (3)	F1 ^x —Rb1—F1 ^{xii}	65.8 (2)
F1 ⁱⁱⁱ —Re1—F1 ^v	93.5 (3)	F1 ^{xi} —Rb1—F1 ^{xiii}	62.7 (2)
F1 ^{iv} —Re1—F1 ^v	180.0	F1 ^x —Rb1—F1 ^{xiii}	128.31 (8)
F1 ⁱ —Re1—F1	180.0	F1 ^{xii} —Rb1—F1 ^{xiii}	96.30 (14)

F1 ⁱⁱ —Re1—F1	86.5 (3)	F1 ^{xi} —Rb1—F1 ^{xiv}	62.7 (2)
F1 ⁱⁱⁱ —Re1—F1	93.5 (3)	F1 ^x —Rb1—F1 ^{xiv}	96.30 (14)
F1 ^{iv} —Re1—F1	86.5 (3)	F1 ^{xii} —Rb1—F1 ^{xiv}	128.31 (8)
F1 ^v —Re1—F1	93.5 (3)	F1 ^{xiii} —Rb1—F1 ^{xiv}	56.0 (3)
F1 ⁱ —Re1—Rb1 ⁱ	53.64 (2)	F1 ^{xi} —Rb1—F1 ^v	96.30 (14)
F1 ⁱⁱ —Re1—Rb1 ⁱ	125.2 (2)	F1 ^x —Rb1—F1 ^v	128.31 (8)
F1 ⁱⁱⁱ —Re1—Rb1 ⁱ	54.8 (2)	F1 ^{xii} —Rb1—F1 ^v	62.7 (2)
F1 ^{iv} —Re1—Rb1 ⁱ	53.64 (2)	F1 ^{xiii} —Rb1—F1 ^v	63.1 (3)
F1 ^v —Re1—Rb1 ⁱ	126.36 (2)	F1 ^{xiv} —Rb1—F1 ^v	118.68 (6)
F1—Re1—Rb1 ⁱ	126.36 (2)	F1 ^{xi} —Rb1—F1 ^{xv}	96.30 (14)
F1 ⁱ —Re1—Rb1 ^{vi}	125.2 (2)	F1 ^x —Rb1—F1 ^{xv}	62.7 (2)
F1 ⁱⁱ —Re1—Rb1 ^{vi}	53.64 (2)	F1 ^{xii} —Rb1—F1 ^{xv}	128.31 (8)
F1 ⁱⁱⁱ —Re1—Rb1 ^{vi}	126.36 (2)	F1 ^{xiii} —Rb1—F1 ^{xv}	118.68 (5)
F1 ^{iv} —Re1—Rb1 ^{vi}	53.64 (2)	F1 ^{xiv} —Rb1—F1 ^{xv}	63.1 (3)
F1 ^v —Re1—Rb1 ^{vi}	126.36 (2)	F1 ^v —Rb1—F1 ^{xv}	166.2 (3)
F1—Re1—Rb1 ^{vi}	54.8 (2)	F1 ^{xi} —Rb1—F1 ^{xvi}	128.31 (8)
Rb1 ⁱ —Re1—Rb1 ^{vi}	106.77 (3)	F1 ^x —Rb1—F1 ^{xvi}	62.7 (2)
F1 ⁱ —Re1—Rb1 ^{vii}	54.8 (2)	F1 ^{xii} —Rb1—F1 ^{xvi}	96.30 (14)
F1 ⁱⁱ —Re1—Rb1 ^{vii}	126.36 (2)	F1 ^{xiii} —Rb1—F1 ^{xvi}	166.2 (3)
F1 ⁱⁱⁱ —Re1—Rb1 ^{vii}	53.64 (2)	F1 ^{xiv} —Rb1—F1 ^{xvi}	118.68 (6)
F1 ^{iv} —Re1—Rb1 ^{vii}	126.36 (2)	F1 ^v —Rb1—F1 ^{xvi}	118.68 (5)
F1 ^v —Re1—Rb1 ^{vii}	53.64 (2)	F1 ^{xv} —Rb1—F1 ^{xvi}	56.0 (3)
F1—Re1—Rb1 ^{vii}	125.2 (2)	F1 ^{xi} —Rb1—F1	128.31 (8)
Rb1 ⁱ —Re1—Rb1 ^{vii}	73.23 (3)	F1 ^x —Rb1—F1	96.30 (14)
Rb1 ^{vi} —Re1—Rb1 ^{vii}	180.0	F1 ^{xii} —Rb1—F1	62.7 (2)
F1 ⁱ —Re1—Rb1	126.36 (2)	F1 ^{xiii} —Rb1—F1	118.68 (6)
F1 ⁱⁱ —Re1—Rb1	54.8 (2)	F1 ^{xiv} —Rb1—F1	166.2 (3)
F1 ⁱⁱⁱ —Re1—Rb1	125.2 (2)	F1 ^v —Rb1—F1	56.0 (3)
F1 ^{iv} —Re1—Rb1	126.36 (2)	F1 ^{xv} —Rb1—F1	118.68 (5)
F1 ^v —Re1—Rb1	53.64 (2)	F1 ^{xvi} —Rb1—F1	63.1 (3)
F1—Re1—Rb1	53.64 (2)	F1 ^{xi} —Rb1—F1 ^{xvii}	104.5 (2)
Rb1 ⁱ —Re1—Rb1	180.0	F1 ^x —Rb1—F1 ^{xvii}	144.30 (9)
Rb1 ^{vi} —Re1—Rb1	73.23 (3)	F1 ^{xii} —Rb1—F1 ^{xvii}	144.30 (9)
Rb1 ^{vii} —Re1—Rb1	106.77 (3)	F1 ^{xiii} —Rb1—F1 ^{xvii}	52.0 (2)
F1 ⁱ —Re1—Rb1 ^{viii}	126.36 (2)	F1 ^{xiv} —Rb1—F1 ^{xvii}	52.0 (2)
F1 ⁱⁱ —Re1—Rb1 ^{viii}	126.36 (2)	F1 ^v —Rb1—F1 ^{xvii}	85.74 (14)
F1 ⁱⁱⁱ —Re1—Rb1 ^{viii}	53.64 (2)	F1 ^{xv} —Rb1—F1 ^{xvii}	85.74 (14)
F1 ^{iv} —Re1—Rb1 ^{viii}	54.8 (2)	F1 ^{xvi} —Rb1—F1 ^{xvii}	114.25 (9)
F1 ^v —Re1—Rb1 ^{viii}	125.2 (2)	F1—Rb1—F1 ^{xvii}	114.25 (9)
F1—Re1—Rb1 ^{viii}	53.64 (2)	F1 ^{xi} —Rb1—F1 ⁱⁱ	144.30 (9)
Rb1 ⁱ —Re1—Rb1 ^{viii}	73.23 (3)	F1 ^x —Rb1—F1 ⁱⁱ	144.30 (9)
Rb1 ^{vi} —Re1—Rb1 ^{viii}	73.23 (3)	F1 ^{xii} —Rb1—F1 ⁱⁱ	104.5 (2)
Rb1 ^{vii} —Re1—Rb1 ^{viii}	106.77 (3)	F1 ^{xiii} —Rb1—F1 ⁱⁱ	85.74 (14)
Rb1—Re1—Rb1 ^{viii}	106.77 (3)	F1 ^{xiv} —Rb1—F1 ⁱⁱ	114.25 (9)
F1 ⁱ —Re1—Rb1 ^{ix}	53.64 (2)	F1 ^v —Rb1—F1 ⁱⁱ	52.0 (2)
F1 ⁱⁱ —Re1—Rb1 ^{ix}	53.64 (2)	F1 ^{xv} —Rb1—F1 ⁱⁱ	114.25 (9)
F1 ⁱⁱⁱ —Re1—Rb1 ^{ix}	126.36 (2)	F1 ^{xvi} —Rb1—F1 ⁱⁱ	85.74 (14)
F1 ^{iv} —Re1—Rb1 ^{ix}	125.2 (2)	F1—Rb1—F1 ⁱⁱ	52.0 (2)

F1 ^v —Re1—Rb1 ^{ix}	54.8 (2)	F1 ^{xvii} —Rb1—F1 ⁱⁱ	62.2 (2)
F1—Re1—Rb1 ^{ix}	126.36 (2)	F1 ^{xi} —Rb1—F1 ^{vi}	144.30 (9)
Rb1 ⁱ —Re1—Rb1 ^{ix}	106.77 (3)	F1 ^x —Rb1—F1 ^{vi}	104.5 (2)
Rb1 ^{vi} —Re1—Rb1 ^{ix}	106.77 (3)	F1 ^{xii} —Rb1—F1 ^{vi}	144.30 (9)
Rb1 ^{vii} —Re1—Rb1 ^{ix}	73.23 (3)	F1 ^{xiii} —Rb1—F1 ^{vi}	114.25 (9)
Rb1—Re1—Rb1 ^{ix}	73.23 (3)	F1 ^{xiv} —Rb1—F1 ^{vi}	85.74 (14)
Rb1 ^{viii} —Re1—Rb1 ^{ix}	180.0	F1 ^v —Rb1—F1 ^{vi}	114.25 (9)
Re1—F1—Rb1 ^x	161.6 (3)	F1 ^{xv} —Rb1—F1 ^{vi}	52.0 (2)
Re1—F1—Rb1	95.10 (14)	F1 ^{xvi} —Rb1—F1 ^{vi}	52.0 (2)
Rb1 ^x —F1—Rb1	83.70 (14)	F1—Rb1—F1 ^{vi}	85.74 (14)
Re1—F1—Rb1 ^{viii}	95.10 (14)	F1 ^{xvii} —Rb1—F1 ^{vi}	62.2 (2)
Rb1 ^x —F1—Rb1 ^{viii}	83.70 (14)	F1 ⁱⁱ —Rb1—F1 ^{vi}	62.2 (2)

Symmetry codes: (i) $-x, -y, -z$; (ii) $x-y, x, -z$; (iii) $-x+y, -x, z$; (iv) $y, -x+y, -z$; (v) $-y, x-y, z$; (vi) $-x+1, -y+1, -z$; (vii) $x-1, y-1, z$; (viii) $x, y-1, z$; (ix) $-x, -y+1, -z$; (x) $-x+1, -y+1, -z+1$; (xi) $y, -x+y+1, -z+1$; (xii) $x-y, x, -z+1$; (xiii) $-x+y, -x+1, z$; (xiv) $x, y+1, z$; (xv) $-y+1, x-y+1, z$; (xvi) $-x+y+1, -x+1, z$; (xvii) $y, -x+y+1, -z$.

Dicaesium hexafluoridorhenate(IV) (SMB_Cs2ReF6_1a)

Crystal data

Cs₂[ReF₆]

$M_r = 566.02$

Trigonal, $P\bar{3}m1$

$a = 6.268$ (1) Å

$c = 4.931$ (1) Å

$V = 167.77$ (6) Å³

$Z = 1$

$F(000) = 239$

$D_x = 5.602$ Mg m⁻³

Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 135 reflections

$\theta = 3.8\text{--}32.6^\circ$

$\mu = 28.83$ mm⁻¹

$T = 100$ K

Hexagonal plate, clear colourless

0.25 × 0.12 × 0.11 mm

Data collection

Bruker D8 QUEST

diffractometer

Radiation source: sealed tube, Siemens

KFFMo2K-90

Curved graphite monochromator

Detector resolution: 8.3333 pixels mm⁻¹

φ and ω scans

Absorption correction: multi-scan

(SADABS; Bruker, 2015)

$T_{\min} = 0.05$, $T_{\max} = 0.15$

2683 measured reflections

218 independent reflections

218 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.040$

$\theta_{\max} = 30.4^\circ$, $\theta_{\min} = 3.8^\circ$

$h = -8 \rightarrow 8$

$k = -8 \rightarrow 8$

$l = -7 \rightarrow 7$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.013$

$wR(F^2) = 0.036$

$S = 1.25$

218 reflections

13 parameters

0 restraints

Primary atom site location: structure-invariant

direct methods

Secondary atom site location: difference Fourier

map

$w = 1/[\sigma^2(F_o^2) + (0.0181P)^2 + 0.1419P]$

where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} < 0.001$

$\Delta\rho_{\max} = 0.68$ e Å⁻³

$\Delta\rho_{\min} = -2.92$ e Å⁻³

Extinction correction: SHELXL2014

(Sheldrick, 2015)

Extinction coefficient: 0.029 (2)

Special details

Geometry. All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Re1	0	0	0	0.00427 (15)
F1	0.3027 (3)	0.15135 (17)	0.2165 (4)	0.0092 (4)
Cs1	0.3333	0.6667	0.30027 (9)	0.00615 (14)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Re1	0.00483 (16)	0.00483 (16)	0.0032 (2)	0.00241 (8)	0	0
F1	0.0088 (8)	0.0107 (6)	0.0075 (9)	0.0044 (4)	-0.0023 (6)	-0.0012 (3)
Cs1	0.00661 (16)	0.00661 (16)	0.0052 (2)	0.00331 (8)	0	0

Geometric parameters (\AA , $^\circ$)

Re1—F1 ⁱ	1.9594 (18)	F1—Cs1 ^{viii}	3.1655 (6)
Re1—F1 ⁱⁱ	1.9594 (18)	F1—Cs1 ^{vi}	3.224 (2)
Re1—F1 ⁱⁱⁱ	1.9594 (18)	Cs1—F1 ^{xi}	3.0955 (19)
Re1—F1 ^{iv}	1.9594 (18)	Cs1—F1 ^x	3.0955 (19)
Re1—F1 ^v	1.9594 (18)	Cs1—F1 ^{xii}	3.0955 (19)
Re1—F1	1.9594 (18)	Cs1—F1 ^{xiii}	3.1655 (6)
Re1—Cs1 ⁱ	3.9100 (6)	Cs1—F1 ^{xiv}	3.1655 (6)
Re1—Cs1 ^{vi}	3.9100 (6)	Cs1—F1 ⁱⁱⁱ	3.1655 (6)
Re1—Cs1 ^{vii}	3.9100 (6)	Cs1—F1 ^{xv}	3.1655 (6)
Re1—Cs1	3.9100 (6)	Cs1—F1 ^{xvi}	3.1655 (6)
Re1—Cs1 ^{viii}	3.9100 (6)	Cs1—F1 ^{xvii}	3.224 (2)
Re1—Cs1 ^{ix}	3.9100 (6)	Cs1—F1 ^{iv}	3.224 (2)
F1—Cs1 ^x	3.0955 (19)	Cs1—F1 ^{vi}	3.224 (2)
F1—Cs1	3.1655 (6)		
F1 ⁱ —Re1—F1 ⁱⁱ	93.14 (7)	Cs1—F1—Cs1 ^{viii}	163.82 (6)
F1 ⁱ —Re1—F1 ⁱⁱⁱ	86.86 (7)	Re1—F1—Cs1 ^{vi}	94.78 (7)
F1 ⁱⁱ —Re1—F1 ⁱⁱⁱ	180.00 (4)	Cs1 ^x —F1—Cs1 ^{vi}	102.55 (5)
F1 ⁱ —Re1—F1 ^{iv}	93.14 (7)	Cs1—F1—Cs1 ^{vi}	94.07 (3)
F1 ⁱⁱ —Re1—F1 ^{iv}	93.14 (7)	Cs1 ^{viii} —F1—Cs1 ^{vi}	94.07 (3)
F1 ⁱⁱⁱ —Re1—F1 ^{iv}	86.86 (7)	F1 ^{xi} —Cs1—F1 ^x	67.11 (6)
F1 ⁱ —Re1—F1 ^v	86.86 (7)	F1 ^{xi} —Cs1—F1 ^{xii}	67.11 (6)
F1 ⁱⁱ —Re1—F1 ^v	86.86 (7)	F1 ^x —Cs1—F1 ^{xii}	67.11 (6)
F1 ⁱⁱⁱ —Re1—F1 ^v	93.14 (7)	F1 ^{xi} —Cs1—F1 ^{xiii}	62.38 (6)
F1 ^{iv} —Re1—F1 ^v	180.00 (8)	F1 ^x —Cs1—F1 ^{xiii}	129.122 (17)
F1 ⁱ —Re1—F1	180.0	F1 ^{xii} —Cs1—F1 ^{xiii}	97.70 (3)

F1 ⁱⁱ —Re1—F1	86.86 (7)	F1 ^{xi} —Cs1—F1 ^{xiv}	62.38 (6)
F1 ⁱⁱⁱ —Re1—F1	93.14 (7)	F1 ^x —Cs1—F1 ^{xiv}	97.70 (3)
F1 ^{iv} —Re1—F1	86.86 (7)	F1 ^{xii} —Cs1—F1 ^{xiv}	129.122 (17)
F1 ^v —Re1—F1	93.14 (7)	F1 ^{xiii} —Cs1—F1 ^{xiv}	53.43 (7)
F1 ⁱ —Re1—Cs1 ⁱ	53.533 (6)	F1 ^{xi} —Cs1—F1 ⁱⁱⁱ	97.70 (3)
F1 ⁱⁱ —Re1—Cs1 ⁱ	53.533 (6)	F1 ^x —Cs1—F1 ⁱⁱⁱ	129.122 (17)
F1 ⁱⁱⁱ —Re1—Cs1 ⁱ	126.467 (6)	F1 ^{xii} —Cs1—F1 ⁱⁱⁱ	62.38 (6)
F1 ^{iv} —Re1—Cs1 ⁱ	124.74 (6)	F1 ^{xiii} —Cs1—F1 ⁱⁱⁱ	65.44 (7)
F1 ^v —Re1—Cs1 ⁱ	55.26 (6)	F1 ^{xiv} —Cs1—F1 ⁱⁱⁱ	118.323 (15)
F1—Re1—Cs1 ⁱ	126.467 (6)	F1 ^{xi} —Cs1—F1 ^{xv}	97.70 (3)
F1 ⁱ —Re1—Cs1 ^{vi}	124.74 (6)	F1 ^x —Cs1—F1 ^{xv}	62.38 (6)
F1 ⁱⁱ —Re1—Cs1 ^{vi}	53.533 (6)	F1 ^{xii} —Cs1—F1 ^{xv}	129.122 (17)
F1 ⁱⁱⁱ —Re1—Cs1 ^{vi}	126.467 (6)	F1 ^{xiii} —Cs1—F1 ^{xv}	118.323 (14)
F1 ^{iv} —Re1—Cs1 ^{vi}	53.532 (6)	F1 ^{xiv} —Cs1—F1 ^{xv}	65.44 (7)
F1 ^v —Re1—Cs1 ^{vi}	126.468 (6)	F1 ⁱⁱⁱ —Cs1—F1 ^{xv}	163.82 (6)
F1—Re1—Cs1 ^{vi}	55.26 (6)	F1 ^{xi} —Cs1—F1	129.123 (17)
Cs1 ⁱ —Re1—Cs1 ^{vi}	106.554 (9)	F1 ^x —Cs1—F1	97.70 (3)
F1 ⁱ —Re1—Cs1 ^{vii}	55.26 (6)	F1 ^{xii} —Cs1—F1	62.38 (6)
F1 ⁱⁱ —Re1—Cs1 ^{vii}	126.467 (6)	F1 ^{xiii} —Cs1—F1	118.323 (15)
F1 ⁱⁱⁱ —Re1—Cs1 ^{vii}	53.533 (6)	F1 ^{xiv} —Cs1—F1	163.82 (6)
F1 ^{iv} —Re1—Cs1 ^{vii}	126.468 (6)	F1 ⁱⁱⁱ —Cs1—F1	53.43 (7)
F1 ^v —Re1—Cs1 ^{vii}	53.532 (6)	F1 ^{xv} —Cs1—F1	118.323 (15)
F1—Re1—Cs1 ^{vii}	124.74 (6)	F1 ^{xi} —Cs1—F1 ^{xvi}	129.122 (17)
Cs1 ⁱ —Re1—Cs1 ^{vii}	73.446 (9)	F1 ^x —Cs1—F1 ^{xvi}	62.38 (6)
Cs1 ^{vi} —Re1—Cs1 ^{vii}	180.0	F1 ^{xii} —Cs1—F1 ^{xvi}	97.70 (3)
F1 ⁱ —Re1—Cs1	126.467 (6)	F1 ^{xiii} —Cs1—F1 ^{xvi}	163.82 (6)
F1 ⁱⁱ —Re1—Cs1	126.467 (6)	F1 ^{xiv} —Cs1—F1 ^{xvi}	118.323 (15)
F1 ⁱⁱⁱ —Re1—Cs1	53.533 (6)	F1 ⁱⁱⁱ —Cs1—F1 ^{xvi}	118.323 (15)
F1 ^{iv} —Re1—Cs1	55.26 (6)	F1 ^{xv} —Cs1—F1 ^{xvi}	53.43 (7)
F1 ^v —Re1—Cs1	124.74 (6)	F1—Cs1—F1 ^{xvi}	65.44 (7)
F1—Re1—Cs1	53.533 (6)	F1 ^{xi} —Cs1—F1 ^{xvii}	102.55 (5)
Cs1 ⁱ —Re1—Cs1	180.0	F1 ^x —Cs1—F1 ^{xvii}	143.51 (2)
Cs1 ^{vi} —Re1—Cs1	73.447 (8)	F1 ^{xii} —Cs1—F1 ^{xvii}	143.51 (2)
Cs1 ^{vii} —Re1—Cs1	106.553 (8)	F1 ^{xiii} —Cs1—F1 ^{xvii}	49.86 (5)
F1 ⁱ —Re1—Cs1 ^{viii}	126.467 (6)	F1 ^{xiv} —Cs1—F1 ^{xvii}	49.86 (5)
F1 ⁱⁱ —Re1—Cs1 ^{viii}	55.26 (6)	F1 ⁱⁱⁱ —Cs1—F1 ^{xvii}	85.93 (3)
F1 ⁱⁱⁱ —Re1—Cs1 ^{viii}	124.74 (6)	F1 ^{xv} —Cs1—F1 ^{xvii}	85.93 (3)
F1 ^{iv} —Re1—Cs1 ^{viii}	126.467 (6)	F1—Cs1—F1 ^{xvii}	113.96 (2)
F1 ^v —Re1—Cs1 ^{viii}	53.533 (6)	F1 ^{xvi} —Cs1—F1 ^{xvii}	113.96 (2)
F1—Re1—Cs1 ^{viii}	53.533 (6)	F1 ^{xi} —Cs1—F1 ^{iv}	143.51 (2)
Cs1 ⁱ —Re1—Cs1 ^{viii}	73.447 (8)	F1 ^x —Cs1—F1 ^{iv}	143.51 (2)
Cs1 ^{vi} —Re1—Cs1 ^{viii}	73.447 (9)	F1 ^{xii} —Cs1—F1 ^{iv}	102.55 (5)
Cs1 ^{vii} —Re1—Cs1 ^{viii}	106.553 (9)	F1 ^{xiii} —Cs1—F1 ^{iv}	85.93 (3)
Cs1—Re1—Cs1 ^{viii}	106.553 (9)	F1 ^{xiv} —Cs1—F1 ^{iv}	113.96 (2)
F1 ⁱ —Re1—Cs1 ^{ix}	53.533 (6)	F1 ⁱⁱⁱ —Cs1—F1 ^{iv}	49.86 (5)
F1 ⁱⁱ —Re1—Cs1 ^{ix}	124.74 (6)	F1 ^{xv} —Cs1—F1 ^{iv}	113.96 (2)
F1 ⁱⁱⁱ —Re1—Cs1 ^{ix}	55.26 (6)	F1—Cs1—F1 ^{iv}	49.86 (5)
F1 ^{iv} —Re1—Cs1 ^{ix}	53.533 (6)	F1 ^{xvi} —Cs1—F1 ^{iv}	85.93 (3)

F1 ^v —Re1—Cs1 ^{ix}	126.467 (6)	F1 ^{xvii} —Cs1—F1 ^{iv}	64.10 (5)
F1—Re1—Cs1 ^{ix}	126.467 (6)	F1 ^{xi} —Cs1—F1 ^{vi}	143.51 (2)
Cs1 ⁱ —Re1—Cs1 ^{ix}	106.553 (8)	F1 ^x —Cs1—F1 ^{vi}	102.55 (5)
Cs1 ^{vi} —Re1—Cs1 ^{ix}	106.553 (9)	F1 ^{xii} —Cs1—F1 ^{vi}	143.51 (2)
Cs1 ^{vii} —Re1—Cs1 ^{ix}	73.447 (9)	F1 ^{xiii} —Cs1—F1 ^{vi}	113.96 (2)
Cs1—Re1—Cs1 ^{ix}	73.447 (9)	F1 ^{xiv} —Cs1—F1 ^{vi}	85.93 (3)
Cs1 ^{viii} —Re1—Cs1 ^{ix}	180.0	F1 ⁱⁱⁱ —Cs1—F1 ^{vi}	113.96 (2)
Re1—F1—Cs1 ^x	162.67 (9)	F1 ^{xv} —Cs1—F1 ^{vi}	49.86 (5)
Re1—F1—Cs1	96.61 (3)	F1—Cs1—F1 ^{vi}	85.93 (3)
Cs1 ^x —F1—Cs1	82.30 (3)	F1 ^{xvi} —Cs1—F1 ^{vi}	49.86 (5)
Re1—F1—Cs1 ^{viii}	96.61 (3)	F1 ^{xvii} —Cs1—F1 ^{vi}	64.10 (5)
Cs1 ^x —F1—Cs1 ^{viii}	82.30 (3)	F1 ^{iv} —Cs1—F1 ^{vi}	64.10 (5)

Symmetry codes: (i) $-x, -y, -z$; (ii) $y, -x+y, -z$; (iii) $-y, x-y, z$; (iv) $x-y, x, -z$; (v) $-x+y, -x, z$; (vi) $-x+1, -y+1, -z$; (vii) $x-1, y-1, z$; (viii) $x, y-1, z$; (ix) $-x, -y+1, -z$; (x) $-x+1, -y+1, -z+1$; (xi) $y, -x+y+1, -z+1$; (xii) $x-y, x, -z+1$; (xiii) $-x+y, -x+1, z$; (xiv) $x, y+1, z$; (xv) $-y+1, x-y+1, z$; (xvi) $-x+y+1, -x+1, z$; (xvii) $y, -x+y+1, -z$.